

## HYDROGEN PRODUCTION VIA WATER GAS SHIFT REACTION ON A NICKEL BASED CATALYST

*Erlisa Baraj, Karel Cíahotný, Tomáš Hlinčík, Veronika Šnajdrová*

*Department of Gaseous and Solid Fuels and Air Protection,  
University of Chemistry and Technology Prague, Technická 5, 166 28 Prague 6  
e-mail: Erlisa.Baraj@vscht.cz*

*In this paper the fundamentals of the water gas shift reaction (WGSR) were described. An overview of the most commonly used catalysts for industrial applications as well as catalysts that are being developed are discussed. The main focus of this work was to perform catalytic activity tests for the WGSR in a laboratory apparatus. The tested catalyst was a nickel-based catalyst. Tests were performed using feed gas consisting of 50 mole % carbon dioxide and the balance nitrogen. Catalytic tests proved that the selected nickel-based catalyst was active for the WGSR. However, it was observed that methanation side reaction also took place.*

*Keywords: WGS; catalyst; hydrogen; carbon monoxide; nickel*

Received 7. 11. 2016, accepted 14. 12. 2016


### 1. Introduction

The water gas shift reaction (WGSR) was discovered in 1780 by the Italian scientist Felice Fontana [1]. In the first published reports the process was described as a way of obtaining clean hydrogen from hydrogen containing gas contaminated with carbon monoxide and hydrocarbons. The gas mixture and excess steam were lead over pumice stone impregnated with nickel or cobalt at temperatures between 350 and 450 °C [2]. However, WGSR found its first industrial application only in 1913 as part of the Haber-Bosch process of ammonia manufacture. After several attempts to obtain clean H<sub>2</sub>, including water electrolysis, it was soon realized that the most economically feasible process on such a large scale as ammonia production was the WGSR [3]. The process was perfected in 1915 by converting CO to CO<sub>2</sub> with steam over iron-chromium catalysts. Carbon dioxide was removed from the gas mixture via scrubbing [4].

Hydrogen demand is increasing and is expected to continue rising in its use as a fuel or as feedstock for the chemical and petrochemical industry. The most notable uses of hydrogen are ammonia production (and subsequent fertilizers production) and the processing of crude oil into fuels and high quality chemical products. Additionally, hydrogen is extensively used in metal and glass industry, electronic and food industry [5]. Nowadays hydrogen is becoming an interesting energy carrier as fuel and eventually as a possible substitute in the future to fossil fuels. Currently, can be observed increasing interest in the utilization of hydrogen for fuel cell applications. Moreover it is also anticipated that renewed interest in the Fischer-Tropsch technology will further enhance the demand for hydrogen. Therefore it is crucial to expand current hydrogen production capacity [6].

#### 1.1. Fundamentals of the water gas shift reaction

The WGSR is a reversible exothermic reaction between carbon monoxide and water steam to from carbon dioxide and hydrogen, as depicted in Eq. (1) [7].



The WGS reaction is a catalytic, equilibrium controlled chemical reaction. Since WGSR proceeds without change in the number of moles, pressure does not affect equilibrium. However, up to the equilibrium moment total pressure can positively affect CO conversion since it increases the reaction rate [8].

Reaction equilibrium is mostly a function of temperature. Taking into consideration that WGSR is a mildly exothermic reaction, in order to increase H<sub>2</sub> production and reduce CO content the reaction should be conducted at lower temperatures. However, certain catalysts are not active at lower temperatures. Moreover, often to achieve the required reaction rate higher temperatures are required. Therefore, WGSR is conducted industrially in two stage catalytic converter. The first, high temperature (HT), stage operates at temperatures ranging from 320 to 450 °C. High temperatures favour fast CO conversion. The second stage, low temperature (LT), operates at temperatures ranging from 150 to 250 °C [8-11].

#### 1.2. Catalysts for the water gas shift reaction

A variety of catalysts is capable to catalyse WGSR. The catalyst of choice can differ depending on reaction temperature. The WGSR is readily catalysed by both metal and metal oxides [11]. For industrial applications the WGSR catalysts are divided into two main classes: Fe-based and Cu-based used for HT and LT conversion, respectively [9].

The HT – WGSR is typically carried out using an iron oxide catalyst structurally promoted with chromium oxide. Typical catalyst used in industrial applications contain about 8 wt % Cr<sub>2</sub>O<sub>3</sub> (chromia). The active phase of the catalyst is Fe<sub>3</sub>O<sub>4</sub> (magnetite). The presence of chromia prolongs the catalysts effective lifetime by stabilizing the material and preventing sintering

[12, 13]. Except catalyst stabilization it is believed that chromia, to a lower extent than magnetite, can also catalyse the reaction [14].

The LT – WGSR enhances the process by allowing a higher CO conversion and yields in H<sub>2</sub> production. Industrially the catalyst used in this phase is a mixture of copper and zinc oxide. Quite often Al<sub>2</sub>O<sub>3</sub> (alumina) serves as a support. The catalysts are unstable at high temperature conditions due to Cu sintering. Thus operation temperatures should not exceed 300 °C [15, 16].

Conventionally used catalysts have their advantages and disadvantages. For instance Fe-based catalysts have the advantage of being cheap and stable but the need of high temperatures is their major limitation. On the other hand, Cu-based catalysts have good activity at lower temperatures but are more susceptible to poisoning (due to the presence of sulphur and chlorine compounds) and operate in a limited temperature range due to sintering [6, 8]. Therefore research on catalysts that have higher activity at lower temperatures and improved stability is crucial. Various metals such as cobalt, molybdenum, gold, platinum, rhodium and palladium are being tested [17-22].

In recent years, Au and Pt-based catalysts have received extended attention since they show very high activity at low temperatures and potential stability in oxidizing atmospheres [9]. It is still difficult to establish which metal shows better catalytic activity since most available data are presented for very specific experimental conditions. Platinum based catalysts have received much attention and have been applied for single stage WGS reaction. The support plays an important role especially in single stage WGS. Some of the most commonly used supports for Pt-based catalysts are ceria and zirconia [21, 23]. However it has been pointed out that a well prepared and properly activated Au based catalyst can be at least as active as a Pt-based catalyst [24].

Except having good activity catalysts should also be financially feasible. Nickel is one of the most widely used metals as catalyst since it has a high surface area and is relatively cheap [25]. Taking into account costs and also the need to develop new catalysts that operate at intermediate temperatures nickel based catalysts have been receiving attention [26, 27]. Moreover in bimetallic catalysts the presence of nickel has positively affected catalyst activity in the temperature range 100 to 240 °C [28].

## 2. Experimental

### 2.1. Laboratory apparatus for catalytic activity measurements

A commercial nickel based catalyst was tested in a laboratory apparatus set up in UCT Prague designed to work at temperatures up to 500 °C, pressure up to 8 MPa. For WGSR catalyst testing a model gas mixture containing 50 mole % CO and 50 mole % N<sub>2</sub>. The gas feed pressure ranging from 0.6 to 8 MPa was controlled via an electronic pressure regulator (Bronkhorst High-Tech B.V., Netherlands). Flow measurements and regulation

up to 10 l·min<sup>-1</sup> (100 kPa; 25 °C), were performed via a thermal mass flowmeter (Bronkhorst High-Tech B.V., Netherlands). Manometers were placed upstream and downstream a control needle valve. At all individual sections of the apparatus ball valves were situated that enabled rapid depressurization of the corresponding parts.

Gas feed preheating, in order to prepare for the WGSR, was carried out in a tubular preheater placed in an oven equipped with a temperature regulator CLARE 4.0 (Clasic CZ s.r.o., Czech Republic). The preheater was 80 cm long and had a diameter of 3.5 cm making for a total volume of 0.77 dm<sup>3</sup>. Distilled water, in order to obtain water vapour, was injected via a capillary in the preheater. The preheated gas mixture afterwards flowed to the WGSR reactor. The reactor was a 15 cm long tubular reactor, with a diameter of 3 cm, wall thickness of 4 mm making for a total volume of 106 ml. The reactor was wrapped with a heating wire and was situated inside two stainless steel protective tubes. One of the protective tubes was 18.5 cm long, had a diameter of 10.8 cm and wall thickness of 3 mm. The other protective tube was 18.5 cm long, had a diameter of 11.4 cm and wall thickness of 3 mm.

The produced gas was cooled in a pressure vessel of a total volume of 0.55 dm<sup>3</sup> situated in a water bath F32ME (Julabo GmbH, Germany) set at -2 °C. Excess material condensed in the pressure vessel. In the final part of the apparatus, sampling of produced gas was performed. The scheme of laboratory apparatus is depicted in Fig. 1.

### 2.2. Catalytic activity measurement

In the reactor was placed 100 g of nickel based catalyst. Feed gas flow was set at approximately 8 l·min<sup>-1</sup> (100 kPa; 25 °C). During all experiments the whole apparatus was at pressure. Catalyst activity tests were performed for pressure 0.5, 2, 4 and 6 MPa. Initially the apparatus was heated at 470 °C using ultra clean N<sub>2</sub>. Once the desired temperature was reached feed gas was switched to the model gas mixture consisting of 50 mole % CO and 50 mole % N<sub>2</sub>. At this point apparatus pressure was regulated to the desired pressure (0.5, 2, 4 or 6 MPa). Once pressure was reached water was pumped into the preheater. Water flow was maintained constant at 3.5 l·min<sup>-1</sup>. The WGSR took place at an initial temperature of 470 °C. Subsequently the reaction took place at gradually lower temperature until reaching 150 °C or zero CO conversion. Produced gas was sampled and analysed approximately every 20 °C. During every sampling interval, excess water condensate was pumped out from the pressure vessel.

### 2.3. Catalyst characterization

Elemental analysis was performed via X-ray fluorescence (XRF) on a Spectrometer ARL 9400 XP (Thermo Fischer Scientific Inc., USA). Data analysis via the software Winxrf, was carried out.

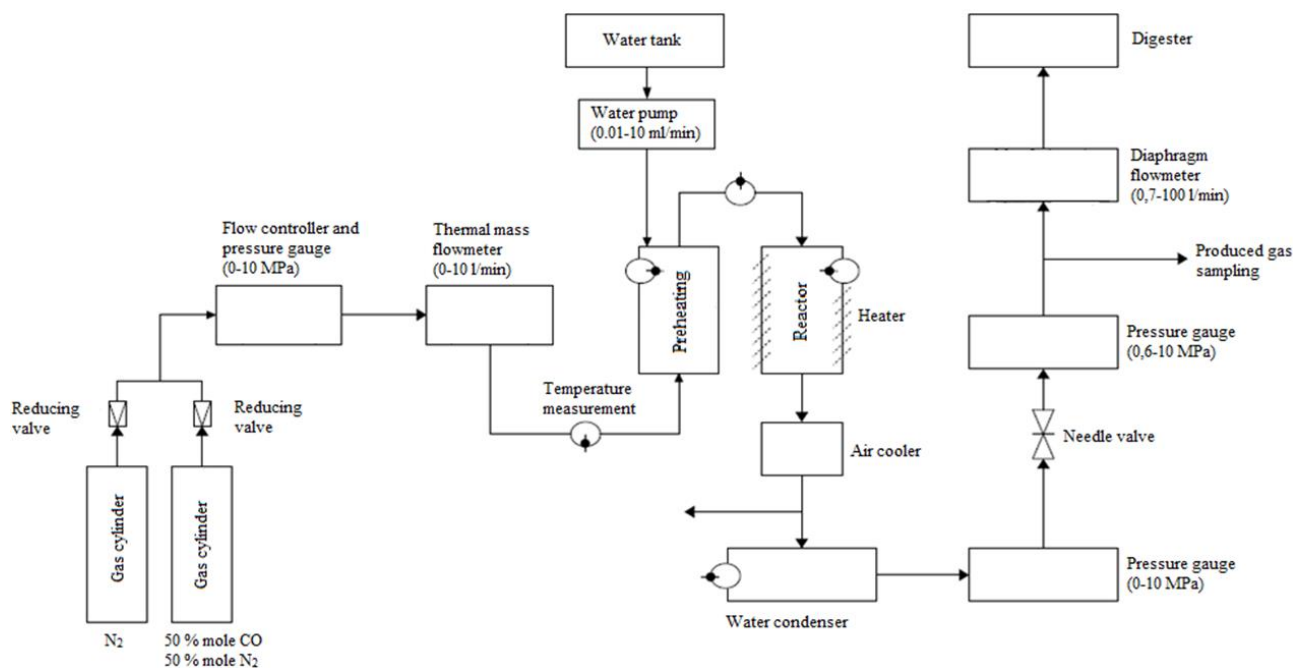


Fig. 1 Laboratory apparatus for the WGSR

Surface area and total pore volume were measured by  $N_2$  adsorption and desorption isotherms at  $-196\text{ }^\circ\text{C}$  using a COULTER SA3100 instrument (Beckman Coulter Inc. USA). Samples were degassed at 13 Pa and  $150\text{ }^\circ\text{C}$ . Surface area was determined based on BET (Brunauer–Emmett–Teller) isotherm measurement. Pore size distribution was calculated based on the BJH (Barrett–Joyner–Halenda) model.

## 2.4. Product analysis

Gaseous products were analysed via a gas chromatograph (GC) Agilent HP 6890 (Agilent Technologies, USA) coupled with a standard flame ionization detector (FID) and a standard thermal conductivity detector (TCD). The GC was fitted with two independent channels in order to make possible the analysis of both organic and inorganic gaseous products in the produced gas. The FID channel permitted the determination of the organic products while the TCD channel permitted the determination of the inorganic products. Since  $H_2$  was one of the compounds of interest, He was chosen as mobile phase.

## 3. Results and discussions

### 3.1. Catalyst characterization

#### *X-ray fluorescence*

X-ray fluorescence analysis of the nickel based catalyst before tests showed that its major component was Ni. Catalyst support was  $SiO_2$ . Nickel content in the catalyst was 74.07 wt % while  $SiO_2$  content was 25.93 wt. %.

#### *BET analysis and pore size distribution*

Catalyst surface area based on BET analysis was  $195.24\text{ m}^2\cdot\text{g}^{-1}$ . Catalyst total pore volume was  $0.3256\text{ ml}\cdot\text{g}^{-1}$ . According to BET theory the adsorption isotherm was type II [29].

#### *Gaseous product analysis*

After GC-FID/TCD analysis of produced gas was established that the WGSR reaction took place in the presence of the nickel based catalyst. Thus the catalyst proved to be active for the WGSR under the described experimental conditions. However except hydrogen and carbon dioxide it was observed that a major component of the produced gas was methane at all applied pressures. The presence of methane indicated that the chosen nickel based catalyst had catalytic activity also for the methanation reaction. In Fig. 2 - Fig. 5 the produced gas compositions for each individual pressure are depicted.

The highest  $CO_2$  content in produced gas, indicating the highest CO conversion rate, was 41.33 mole %. This  $CO_2$  content was achieved under 4MPa pressure and temperature  $433\text{ }^\circ\text{C}$  experimental conditions. However, the highest hydrogen content in the produced gas of 12.1 mole % was observed at 0.5 MPa pressure and temperature  $485\text{ }^\circ\text{C}$ . The highest methane content in the produced gas of over 12 mole % was observed at 4 MPa pressure and in the temperature range from 210 to  $360\text{ }^\circ\text{C}$ . Similar results were also observed for 6 MPa pressure in the temperature range from 260 to  $360\text{ }^\circ\text{C}$ .

From the acquired data it was confirmed that elevated pressure does not positively influence the WGSR.

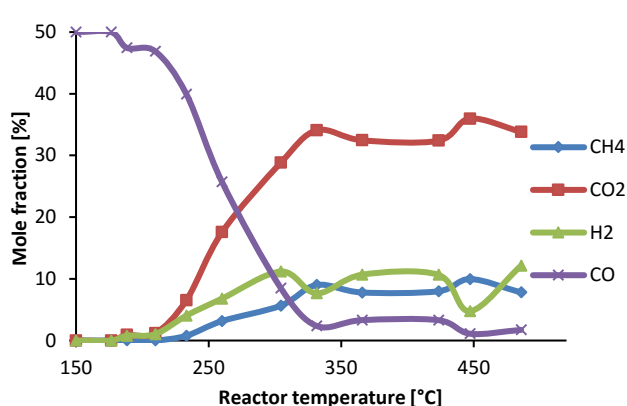


Fig. 2 Produced gas composition at pressure 0.5 MPa.

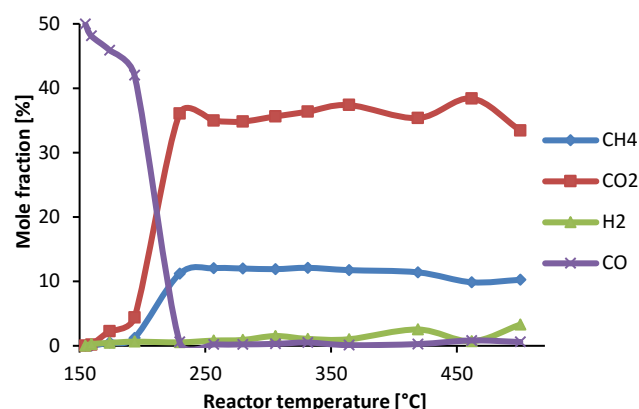


Fig. 5 Produced gas composition at pressure 6 MPa.

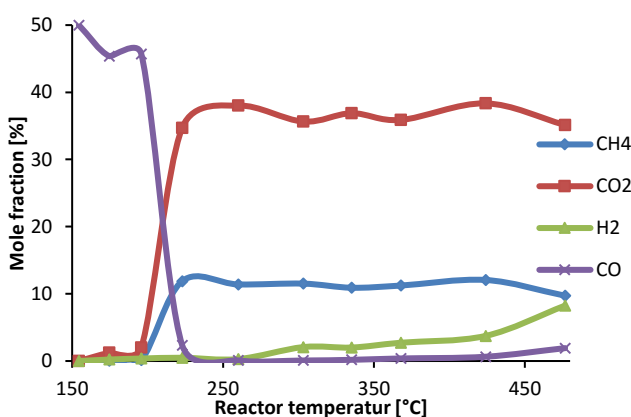


Fig. 3 Produced gas composition at pressure 2 MPa.

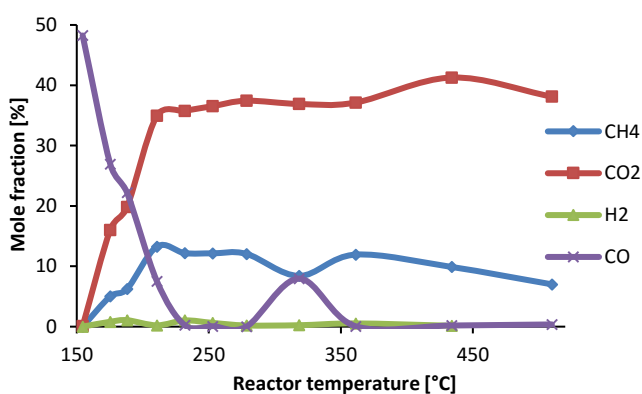


Fig. 4 Produced gas composition at pressure 4 MPa.

On the contrary low hydrogen content along with high methane content at elevated pressure indicated that higher pressure had a positive effect on the methanation reaction. The fact that produced gas composition at 4 and 6 MPa was quite similar indicates that after certain values pressure does no longer play a substantial role for neither WGSR nor methanation reaction.

#### 4. Conclusions

The selected commercial nickel based catalyst proved to be active for the WGSR reaction under the applied laboratory experimental conditions. Experiments were performed using a model gas mixture consisting of 50 mole % CO and 50 mole % N<sub>2</sub>. Tests were performed at 0.5, 2, 4 and 5 MPa pressure and in the temperature range 150 - 470 °C. During the course of the experiments it was observed that in the produced gas was also present methane indicating that the catalyst was active also for the methanation reaction.

The highest conversion rate of CO to CO<sub>2</sub> was 83 % and was reached at 4 MPa pressure and temperature 433 °C. The highest H<sub>2</sub> content of 12.1 mole % was at 0.5 MPa pressure and temperature 485 °C. The highest methane content in the produced gas of over 12 mole % was observed at 4 MPa pressure and in the temperature range from 210 to 360 °C. Similar results were also observed for 6 MPa pressure in the temperature range from 260 to 360 °C.

The acquired data indicated that the produced hydrogen via WGSR immediately reacts with either carbon monoxide or carbon dioxide to form methane. Taking into consideration that elevated pressure positively affects methanation it is only natural that the highest methane content in the produced gas was observed at pressure 4 and 6 MPa.

#### Acknowledgments

The present work was financially supported by TACR – Alfa Project TA04021005 “Nízkoemisní energetický systém se záchytem CO<sub>2</sub> před spalováním”.

#### 5. References

1. Burns, D.T., G. Piccardi, and L. Sabbatini, Some people and places important in the history of analytical chemistry in Italy. *Microchimica Acta*, 2008. 160(1-2): p. 57-87.
2. Mond, L., Process of obtaining hydrogen gas. 1889, British Patent 12608.

3. Basile, A. and A. Iulianelli, *Advances in Hydrogen Production, Storage and Distribution*. 2014: Elsevier Science.
4. Travis, A.S., et al., *Determinants in the Evolution of the European Chemical Industry, 1900–1939: New Technologies, Political Frameworks, Markets and Companies*. 2013: Springer Netherlands.
5. Ball, M., W. Weidorf, and U. Bünger, *Hydrogen production*, in *The Hydrogen Economy: Opportunities and Challenges*, M. Ball and M. Wietschel, Editors. 2009, Cambridge University Press: New York, United States of America.
6. Chaubey, R., et al., A review on development of industrial processes and emerging techniques for production of hydrogen from renewable and sustainable sources. *Renewable and Sustainable Energy Reviews*, 2013. 23: p. 443-462.
7. Smirniotis, P. and K. Gunugunuri, *Water Gas Shift Reaction: Research Developments and Applications*. 2015: Elsevier Science.
8. Newsome, D.S., *The Water-Gas Shift Reaction*. *Catalysis Reviews*, 1980. 21(2): p. 275-318.
9. Mendes, D., et al., The water-gas shift reaction: from conventional catalytic systems to Pd-based membrane reactors—a review. *Asia-Pacific Journal of Chemical Engineering*, 2010. 5(1): p. 111-137.
10. Chen, W.-H. and J.-G. Jheng, Characterization of water gas shift reaction in association with carbon dioxide sequestration. *Journal of Power Sources*, 2007. 172(1): p. 368-375.
11. Grenoble, D.C., M.M. Estadt, and D.F. Ollis, The chemistry and catalysis of the water gas shift reaction: 1. The kinetics over supported metal catalysts. *Journal of Catalysis*, 1981. 67(1): p. 90-102.
12. Rhodes, C., et al., Promotion of Fe<sub>3</sub>O<sub>4</sub>/Cr<sub>2</sub>O<sub>3</sub> high temperature water gas shift catalyst. *Catalysis Communications*, 2002. 3(8): p. 381-384.
13. Maroño, M., et al., Performance of Fe–Cr based WGS catalysts prepared by co-precipitation and oxiprecipitation methods. *International Journal of Hydrogen Energy*, 2009. 34(21): p. 8921-8928.
14. Martos, C., J. Dufour, and A. Ruiz, Synthesis of Fe<sub>3</sub>O<sub>4</sub>-based catalysts for the high-temperature water gas shift reaction. *International Journal of Hydrogen Energy*, 2009. 34(10): p. 4475-4481.
15. Hossain, M.M. and S. Ahmed, Cu-based mixed metal oxide catalysts for WGS: Reduction kinetics and catalytic activity. *The Canadian Journal of Chemical Engineering*, 2013. 91(8): p. 1450-1458.
16. Twigg, M.V. and M.S. Spencer, Deactivation of supported copper metal catalysts for hydrogenation reactions. *Applied Catalysis A: General*, 2001. 212(1–2): p. 161-174.
17. Mellor, J.R., R.G. Copperthwaite, and N.J. Coville, The selective influence of sulfur on the performance of novel cobalt-based water-gas shift catalysts. *Applied Catalysis A: General*, 1997. 164(1–2): p. 69-79.
18. Patt, J., et al., Molybdenum carbide catalysts for water–gas shift. *Catalysis Letters*, 2000. 65(4): p. 193-195.
19. Shido, T. and Y. Iwasawa, Reactant-Promoted Reaction Mechanism for Water-Gas Shift Reaction on Rh-Doped CeO<sub>2</sub>. *Journal of Catalysis*, 1993. 141(1): p. 71-81.
20. Luengnaruemitchai, A., S. Osuwan, and E. Gulari, Comparative studies of low-temperature water–gas shift reaction over Pt/CeO<sub>2</sub>, Au/CeO<sub>2</sub>, and Au/Fe<sub>2</sub>O<sub>3</sub> catalysts. *Catalysis Communications*, 2003. 4(5): p. 215-221.
21. Gonzalez Castaño, M., et al., Pt vs. Au in water–gas shift reaction. *Journal of Catalysis*, 2014. 314(0): p. 1-9.
22. Cornaglia, L., J. Múnera, and E. Lombardo, Recent advances in catalysts, palladium alloys and high temperature WGS membrane reactors: A review. *International Journal of Hydrogen Energy*, 2015. 40(8): p. 3423-3437.
23. Jeong, D.-W., et al., H<sub>2</sub> production from a single stage water–gas shift reaction over Pt/CeO<sub>2</sub>, Pt/ZrO<sub>2</sub>, and Pt/Ce(1-x)Zr(x)O<sub>2</sub> catalysts. *International Journal of Hydrogen Energy*, 2013. 38(11): p. 4502-4507.
24. Burch, R., Gold catalysts for pure hydrogen production in the water-gas shift reaction: activity, structure and reaction mechanism. *Physical Chemistry Chemical Physics*, 2006. 8(47): p. 5483-5500.
25. Vance, C.K. and C.H. Bartholomew, Hydrogenation of carbon dioxide on group viii metals: III, Effects of support on activity/selectivity and adsorption properties of nickel. *Applied Catalysis*, 1983. 7(2): p. 169-177.
26. Fuentes, E.M., et al., A comparison between copper and nickel-based catalysts obtained from hydrotalcite-like precursors for WGS. *Catalysis Today*, 2011. 171(1): p. 290-296.
27. Santos, M.d.S., et al., Effect of aluminum content on the properties of lanthana-supported nickel catalysts to WGS, in *Studies in Surface Science and Catalysis*, M.S. Fábio Bellot Noronha and S.-A. Eduardo Falabella, Editors. 2007, Elsevier. p. 493-498.
28. Venugopal, A., J. Aluha, and M.S. Scurrill, The Water-Gas Shift Reaction Over Au-Based, Bimetallic Catalysts. The Au-M (M=Ag, Bi, Co, Cu, Mn, Ni, Pb, Ru, Sn, Tl) on Iron(III) Oxide System. *Catalysis Letters*, 2003. 90(1): p. 1-6.
29. Sing, K.S.W., Analysis of physisorption isotherms . Determination of surface area and porosity, in *Physical Adsorption: Experiment, Theory and Applications*, J.P. Fraissard and C.C. W., Editors. 1997, Kluwer Academic Publishers: Dordrecht, The Netherlands. p. 9-16.